

# INFLUENCE OF NANOFIBER LOADING AND MOULDING CONDITIONS ON THE JOINING STRENGTH OF THERMOPLASTIC COMPOSITES FABRICATED BY INJECTION OVER-MOULDING PROCESS

KOKI MATSUMOTO<sup>1\*</sup>, TUKASA NAGASAKA<sup>1</sup>, KENICHI TAKEMURA<sup>1</sup> & TATSUYA TANAKA<sup>2</sup>

<sup>1</sup>Department of Mechanical Engineering, Kanagawa University, Japan

<sup>2</sup>Department of Energy and Mechanical Engineering, Doshisha University, Japan

## ABSTRACT

An over-moulding process has promised a novel technology for joining lightweight thermoplastic composites with metal or polymer composite parts. Specifically, the substrate parts (metal or textile composites) are put into a mould of the injection moulding machine and melt polymer is injected onto substrate parts. This over-moulding process provides great benefits in terms of fast welding and moulding at the same time. However, the interfacial joining strength of over-moulded parts is still unreliable, and it has a strong dependence on surface treatment of substrate and moulding conditions. The key topic of this joining process is to achieve a reliable joining strength. In this study, we focused on using cellulose nanofiber (CNF) to interconnect between substrate and injection part by purpose of mechanical interlocking in nanoscale. Furthermore, joining strength was determined by single-lap shear test to examine the effect of presence of nanofiber. The single-lap joint consists of plain weave carbon fibre (CF) reinforced polypropylene (PP) composites (CFRPP) as substrate part and pure PP as over-injection polymer. To place the cellulose nanofiber at the interface, CF wovens and PP sheets were stacked alternately, and CNF contained PP sheet was placed at outer layer. The CFRPP substrate was obtained by heating press, pure PP was injected onto the substrate at the side of presence of CNF. This study was investigated on the influence of process conditions (i.e., injection temperature and runner route) and CNF content ratio (up to 3.0 wt%) on the shear strength as joining strength. Furthermore, the fracture morphology was observed through scanning electron microscope (SEM).

*Keywords:* over-moulding process, cellulose nanofiber, lightweight hybrid composite, single-lap shear.

## 1 INTRODUCTION

In the automotive industry, applying a lightweight structure with excellent mechanical properties is most important approach to reduce the environmental load. Thereby, a demand of carbon fibre (CF) reinforced thermoplastic composites (CFRTPs) has increased every year for mass production due to high mechanical property, recyclability and high productivity. Especially, for purpose of replacing metals to polymer composites, multi-material design by joining of different materials (e.g., CFRTPs and metals) is a new concept to meet the strict environmental regulations [1]–[4]. Furthermore, the combination of plastic processing technologies (e.g., injection moulding, extrusion process, and 3D printing) makes possible to manufacture lightweight design of hybrid CFRTPs with complex shape parts [5]–[11]. Therefore, a lot of thermal joining processes (laser welding [12]–[14], friction welding [15], ultrasonic welding [16] and injection over-moulding [17]–[20]) have been developed for joining thermoplastic composites with other materials.

In injection over-moulding process, direct joining of different components and forming of complex shape could be done at the same time. A substrate parts (e.g., metal parts and CFRTPs) are inserted into the mould of injection moulding machine, and subsequently the

\*ORCID: <https://orcid.org/0000-0002-4220-7304>



melt polymer is injected onto the substrate parts [5]. Direct joining could reduce the weight due to absence of mechanical fasteners (e.g., screws, bolts and rivets) and adhesives. In any case, the most important key of over-moulding process is to achieve a reliable joining strength. In a polymer metal hybrids (HPM), the roughness of metal surface is controlled to mechanically interlock the joining interface. Lucchetta et al. [17] were applied shot peening on the surface of Aluminium (Al) 6082, and glass fibre reinforced polypropylene (PP) was injected onto the Al part. The combination of mechanical interlocking by surface roughness and anchor role by glass fibres could enhance the lap-shear strength. Kimura et al. [18], [19] formed nano-porous structure on the surface of A 5052 Al by chemical etching process, and glass fibre reinforced polybutylene terephthalate (PBT) was moulded onto Al substrate part. They reported nanometer-scale structure enables to increase lap-shear strength by compared with micrometer-scale structure. Even though the surface roughness and nanopatterns [21] enhance the joining strength, the moulding conditions (e.g., injection speed, holding pressure, and resin temperature) have great influence on that.

Furthermore, hybrid thermoplastic composites can be manufactured by combination of continuous fibre reinforced composites and discontinuous fibre reinforced composites through injection over-moulding process. An organosheet, which thermoplastic resin is impregnated into continuous fibre or plain weave fabric, is pre-heated before inserting in the mould of injection moulding. The pre-heated organosheet was thermoformed during closing the mould, and short fibre reinforced thermoplastics injected onto thermoformed part to fabricate the hybrid composites. The joining strength is strongly affected by preheating conditions and moulding conditions [5], [10]. However, only the optimization of these processing parameters can enhance the joining strength. Therefore, new approach is necessary to be a reliable joining strength for hybrid thermoplastic composites without limitation of resin system and injection moulding system.

In the nano-engineered composites (i.e., multiscale composites), Garcia et al. [22] and Wicks et al. [23] focused on grafting carbon nanotubes (CNTs) on the CFs in the radial direction along the fibre. Epoxy resin is reinforced by CNT grafted CF wovens and its interlaminar shear strength (ILSS) was improved by 69%. Veedu et al. [24] reported fracture toughness, mechanical properties, damping property and thermal conductivity of the composite were strongly improved by grafted CNT on CF. Adding of functional nanofiller at conventional textile composite provides some functional properties at low contents of nanofillers. Furthermore, Matsumoto et al. [25] added the CNTs at joining interface between organosheet and injection polymer through injection over-moulding process. Even though the dispersion state of CNTs affected on joining strength, the ILSS was increased up to 52% by adding CNTs of 1 wt%. This means the nanotubes have ability to interconnect the different layers. However, there is a few reports of using nanofillers on application for joining technologies.

In this study, we newly attempt to use cellulose nanofibers (CNFs) on joining technologies, especially for hybrid thermoplastic composites through injection over-moulding process. CNFs have excellent mechanical properties and eco-friendly material. During fabrication of substrate parts which consist of CF wovens and PP films, CNFs filled PP sheet was placed at joining side. After impregnation and consolidation were finished during compression moulding, the substrate of CF woven reinforced PP composite (CFRPP) was obtained. Afterwards, CNF contained CFRPP substrate was inserted into the mould of injection moulding machine. The pure PP (without short fibres) was chosen as injection polymer to evaluate the simply effect of CNFs on joining strength. Finally, pure PP was injected onto the substrate part at side of presence of CNFs, and moulded specimens are obtained as single-lap joints. The joining strength was determined by single-lap shear test. In this paper, the



influence of moulding conditions (i.e., barrel temperature and runner route) and CNF loading (up to 3 wt%) on lap-shear strength was investigated. Moreover, fracture morphology was observed through scanning electron microscope (SEM) to discuss the interconnection role of CNFs.

## 2 EXPERIMENTAL PROCEDURES

### 2.1 Materials

Plain weave CF (Torayca<sup>®</sup> cloth type CO6343) was purchased from Toray Industries Inc., Japan and PP (Prime Polypro<sup>™</sup> type J107G) was purchased from Prime Polymer Co. Ltd, Japan. The PP is homopolymer and a melt flow rate is 30 g/10 min (230°C, 2.16 kg). A cellulose nanofiber (BiNF-i-s type WFo-10005) was purchased from Sugino Machine Co. Ltd, Japan. The average diameter of this CNFs is approximately 10–50 nm and specific surface area is 120 m<sup>2</sup>/g.

### 2.2 Fabrication of single-lap joint

At the beginning, a CNFs filled CFRPP substrates were fabricated. The CF woven sheets (150 mm × 150 mm size) and pure PP or CNF filled PP (CNF/PP) sheets were prepared. The pure PP sheets and CNF/PP sheets were manufactured by heat press (Mini Test Press type MP-WCL) from Toyo Seiki Seisaku-Sho Ltd, Japan. Before compression of the nanocomposite lump that CNFs loading in weight were controlled by extruder, the lumps were pre-heated at 180°C for 4 min. The pre-heated lumps were compressed at pressure of 3.0 MPa for 3 min at the same temperature, followed by cooling to 30°C rapidly. The thickness of obtained sheets was approximately 200 μm and CNF loading set as 0 wt%, 0.5 wt%, 1.0 wt%, 3.0 wt%. After that, obtained seven pure PP sheets and seven CF woven sheets were stacked alternately, the CNF/PP sheets were placed at outer layer on only one side. The stack was pre-heated at 190°C for 10 min and compressed at pressure of 1.0 MPa (190°C, 15 min) while vacuuming air. The obtained CNF filled CFRPPs substrates had thickness of 3 mm and cut into small specimens (50 mm in length and 10 mm in width).

The fabrication of single-lap joint was conducted by injection moulding machine (type EC5P-0.1B) from Toshiba Machine Co. Ltd, Japan. The mould was originally self-designed for fabrication of the single-lap joint, and the runner route could be changed. The route A describes melt polymer flows into the opposite position of joining area. Other hands, the route B describes melt polymer flows from the joining area. The obtained substrate was inserted in the mould and pure PP was injected onto the substrate part at the side of presence of CNFs. The dimension of single-lap joint was described in Fig. 1(a), and moulded single-lap joint fabricated by each runner route was shown in Fig. 1(b). The dimension of substrate part and injection part was same and joining area was 12.5 mm in length and 10 mm in width. The moulding conditions are listed in Table 1. In this paper, two parameters (runner route and barrel temperature) were changed for fabricating specimens of single-lap joint. In addition, the barrel temperature was varied from 200°C, 220°C, 240°C, 260°C.

### 2.3 Single-lap shear test

To evaluate the joining strength as lap-shear strength, tensile shear test was carried out by universal testing machine (type AG-IS) from Shimadzu Corporation, Japan. PP tabs (25 mm in length, 10 mm in width and 3 mm in thickness) were welded along the edge of specimen



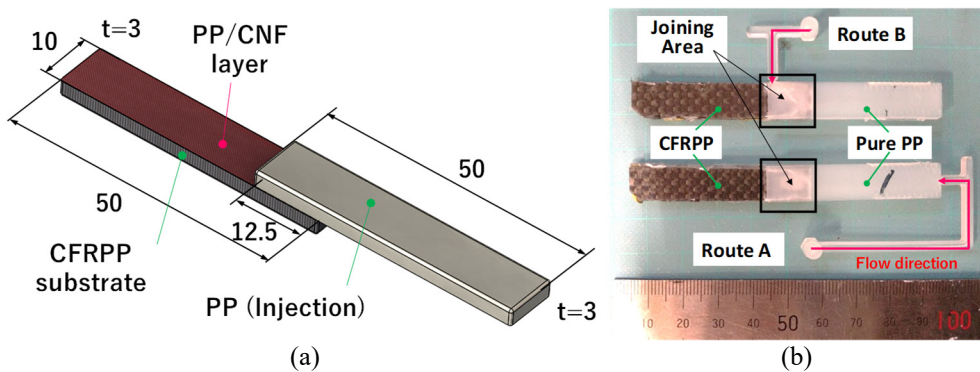


Figure 1: Single-lap joint. (a) A schematic drawing of specimen and dimension; and (b) Moulded specimens by changing runner route (lower: route A and upper: route B).

Table 1: Moulding conditions of injection over-moulding.

Process parameter	Set value			
	Route A		Route B	
Runner route	Route A		Route B	
Screw speed (rpm)	100			
Injection speed (mm/s)	30			
Back pressure (MPa)	2.0			
Barrel temperature (°C)	200	220	240	260
Mould temperature (°C)	60			
Holding pressure (MPa)	40 (1st)/10 (2nd)			
Holding time (s)	15 (1st)/5 (2nd)			
Cooling time (s)	20			

by soldering iron. The tensile shear test was conducted at a cross head speed of 1 mm/min for three samples at each condition. The overview of tensile shear test was shown in Fig. 2. The lap-shear strength is obtained by dividing failure load by joining area.

#### 2.4 Observation of fracture morphology

The fracture morphology was observed by using field emission scanning electron microscope (FE-SEM) (type S-4000) from Hitachi Ltd, Japan. The peeled surfaces of substrate and injection PP were mainly observed after lap-shear test. The peeled surfaces were coated by gold through sputtering system (Desk Top Quick Coater type SC-701MkII) from Sanyu Electron Co. Ltd, Japan. The state of CNFs at peeled surfaces was also observed.

### 3 RESULTS AND DISCUSSION

#### 3.1 Load-displacement curve of lap-shear test

Before discussing effect of CNFs on lap-shear strength, the pure influence of process conditions was simply discussed here for the material system without CNFs. The load-

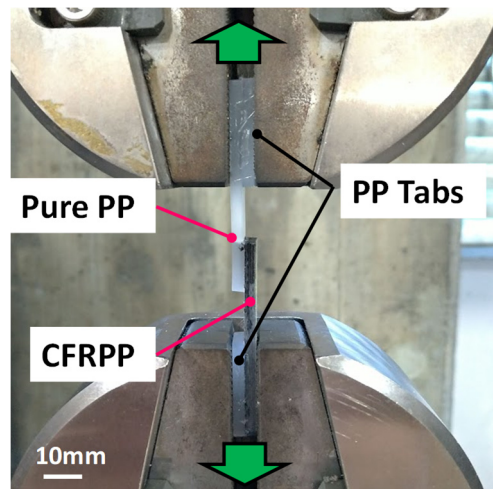


Figure 2: Over viewing of tensile shear test for specimen of single-lap joint.

displacement curves of lap-shear test and failure mode are shown in Fig. 3 (dotted area shows peeled position). Fig. 3(a) represents the influence of barrel temperature for the specimens which are moulded in runner route A, and Fig. 3(b) is for runner route B. As a reference material, PP injected into mould without insert substrate, it denotes as “all injected PP” in Fig. 3.

The “all injected PP” samples have no joining interface. Therefore, maximum of apparent shear strength of pure PP could be estimated. However, please note that the edge of lap joint rotates by bending moment and peel stress is caused [2], [4]. Therefore, the failure load of “all injected PP” samples does not indicate shear strength exactly. As the pictures of fracture mode are listed in Fig. 3, “all injected PP” samples were broken at step where thickness is changed due to stress concentration. The apparent shear strength of PP is only a guide for judging joining strength by injection over-moulding process was enough or not. The slope of load-displacement curve in “all injected PP” sample is lower than over-moulded samples. This explains that CFRPP has higher flexural modulus by compared with PP.

In this experiment, the condition of barrel temperature of 260°C and route A showed the highest failure load. In the influence of barrel temperature, failure load and displacement at break were increased with higher barrel temperature regardless of runner route. In the theory, welding should be done by diffusion of molecular chain between injection PP and PP layer of substrate. Therefore, molecular diffusion is affected by resin temperature at joining area during injection moulding. As shown in Fig. 3, the failure load of over-moulded specimens was smaller than that of “all injected PP” specimens even though barrel temperature is quite higher than melting temperature of PP (approximately 165°C) with excepting condition at 260°C in route A. It is assumed that resin temperature dropped down dramatically before injection PP reached to joining area, and molecular diffusion didn't complete.

Additionally, this molecular diffusion could be affected by runner route because the runner distance of route B (approximately 23.5 mm) is quite shorter than route A (approximately 68.0 mm). In case of injection speed of 30 mm/s, the difference of time was about 0.3 s by calculation from volume flow rate. Thus, route B has possibility to keep higher

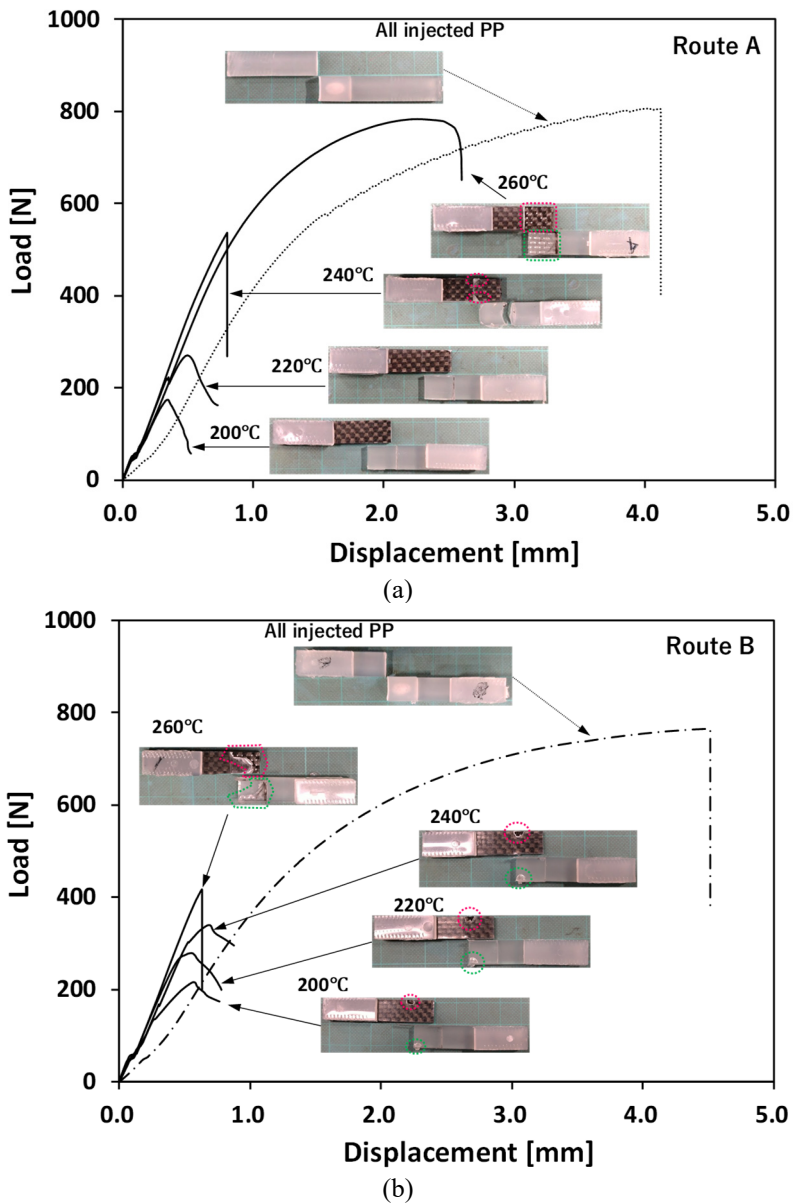


Figure 3: Load-displacement curve and fracture mode of over-moulded specimens without CNFs. (a) Specimens moulded in route A; and (b) Specimens moulded in route B.

resin temperature at joining area by compared with route A. However, interestingly, increasing rate of failure load in route B was smaller than that in route A by increasing barrel temperature. A part of PP layer in the substrate was peeled at only the entrance of gate position for the conditions at barrel temperature of 200°C, 220°C, 240°C through route B.

Moreover, for the condition at barrel temperature of 260°C and route B, the peeled shape was unique as shown in Fig. 3(b). Whereas, the PP layer of joining area was completely peeled at same temperature through route A, as shown in Fig. 3(a).

This reason why, flow behaviour in the mould affected on the lap-shear strength. The velocity field of route A may have the laminar flow while the PP is filled in the mould. Other hands, flow behaviour of route B shows the corner flow. Kimura et al. [18] examined the same influence of runner route, and orientation of glass fibre in injection resin was observed through X-ray tomography. The glass fibres aligned as curve shape along the flow path which melted polymer composites enter from the side of joining area (like route B in this experiment). Therefore, the peeled shape (at 260°C, route B) corresponds to flow shape and the diffusion welding did not conduct uniformly. However, route B has higher failure load at 200°C and 220°C by compared with route A at same temperature. Thus, the optimization of gate position in route B could improve the joining strength. From these reasons, keeping high temperature above melt temperature and uniform velocity field for constant temperature distribution during injection moulding should be realized to obtain the excellent lap-shear strength. The resin temperature at joining area is also affected by injection speed. The optimum resin temperature at joining interface should be discussed in the mould during injection moulding by using numerical simulation and in-line sensors in further discussion.

### 3.2 Influence of CNF addition on lap-shear strength

In this section, the influence of CNFs addition on joining strength is discussed. The effect of CNF addition on lap-shear strength may display after molecular diffusion was completed since CNFs exist in the PP layer of substrate. The results of averaged shear strength and displacement at break by adding CNFs were summarized in Fig. 4 for specimens moulded through route A and Fig. 5 for specimens moulded through route B.

In route A (see in Fig. 4), above barrel temperature of 240°C, lap-shear strength and displacement at break increased by adding CNFs up to 1.0 wt%. By compared with samples without CNFs, the lap-shear strength and displacement at break are improved by 32% and 54% respectively at barrel temperature of 240°C, and those are improved by 12% and 85% respectively at barrel temperature of 260°C. However, by adding CNFs of 3.0 wt%, the lap-shear strength and displacement at break were decreased or almost same value. As we already

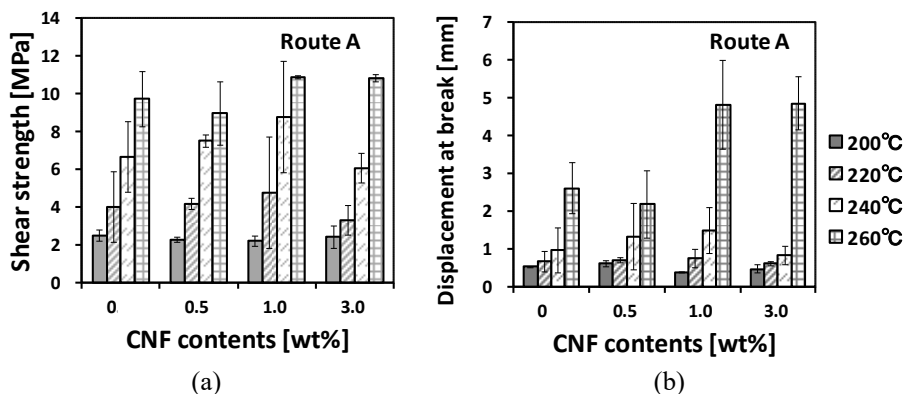


Figure 4: The results of lap shear test at various CNF loading and barrel temperature through route A. (a) lap-shear strength; (b) displacement at break.

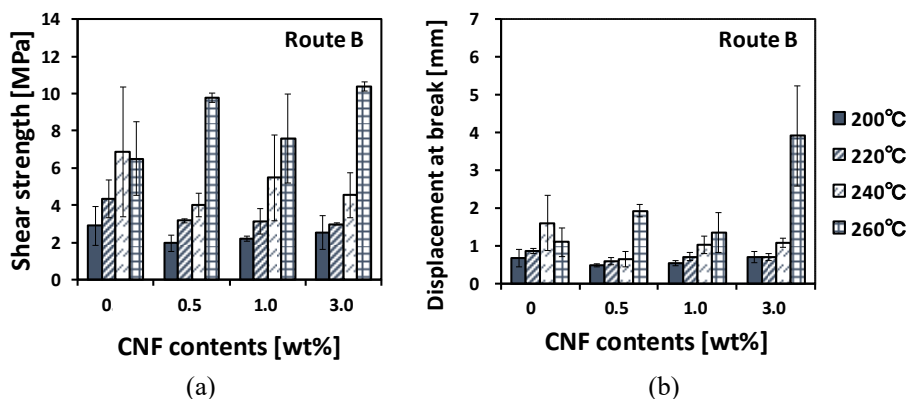


Figure 5: The results of lap-shear test at various CNF loading and barrel temperature through route B. (a) lap-shear strength; (b) displacement at break.

discussed in our previous work [25], this reason why dispersion state of nanofibers greatly affected on the joining strength. The agglomeration of nanofibers may be weak point during lap-shear test. Therefore, dispersion of CNFs still should be improved during mixing by compounder.

In route B (see in Fig. 5), at only barrel temperature of 260°C, lap-shear strength and displacement at break increased by adding CNFs up to 3.0 wt%. This result was completely different with result of route A. At that condition, the lap-shear strength and displacement at break were increased by 60% and 357% respectively. However, these values were lower than those values in route A at same temperature. This reason was already discussed in Section 3.1, the flow behaviour at joining area affected on molecular diffusion. Thus, CNFs could perform as interconnection role at only partially bonded area, uniform bonding state should be necessary to improve the joining strength. From these results, we found that CNFs have ability to improve the lap-shear strength at specific conditions. The optimum barrel temperature (at least above 240°C) and uniform temperature distribution are necessary to get the interconnection ability of CNFs on joining strength.

Finally, the fracture modes are summarized in Table 2 for route A and Table 3 for route B. The fracture modes were categorized as follows: (a) interfacial failure between substrate and injection resin (i.e., not bonding), (b) partially or fully substrate failure of resin layer, and (c) flexure failure at side of injected PP. The examples of these fracture modes are shown in Fig. 6. The fracture modes are completely linked to lap-shear strength. Especially, at barrel temperature of 260°C, fracture mode was shifted from type (b) to type (c) with increasing CNF loading. According to fracture type of “all injected PP” samples as shown in Fig. 3, fracture mode of type (c) shows maximum lap-shear strength. Therefore, CNFs absolutely improve the joining strength after polymer diffusion is completely done.

### 3.3 Fracture morphology

The fracture morphology of over-moulded specimens after lap-shear test was observed by FE-SEM. To confirm the presence of CNFs at joining area, the peeled surfaces were observed in samples which were fractured in type (b) in Fig. 6. Fig. 7 shows peeled surfaces of over-



Table 2: Failure mode of specimens moulded in route A.

Barrel temp. (°C)	CNF loading (wt%)			
	0	0.5	1.0	3.0
200	(a)	(a)	(a)	(a)
220	(a)	(a)	(a)	(a)
240	(a), (b)	(b)	(b)	(a)
260	(b)	(b), (c)	(b), (c)	(c)

Table 3: Failure mode of specimens moulded in route B.

Barrel temp. (°C)	CNF loading (wt%)			
	0	0.5	1.0	3.0
200	(b)	(b)	(b)	(b)
220	(b)	(b)	(b)	(b)
240	(b)	(b)	(b)	(b)
260	(b)	(b), (c)	(b), (c)	(c)

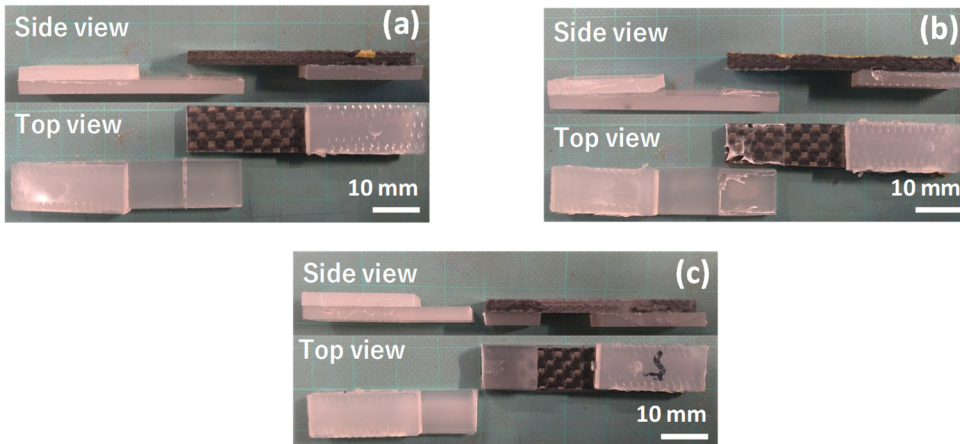


Figure 6: Fracture modes after lap-shear test. (a) Interfacial failure between substrate and injection PP; (b) Substrate failure of resin layer; and (c) Flexure failure at injection PP.

moulded sample without CNFs that moulded at barrel temperature of 260°C through route A on the both side (i.e. substrate side and injected PP side). At the aperture of plain weave in substrate part, the PP was confirmed and deformed along the shear direction. Moreover, the shear deformation of PP was confirmed on the side of injection PP as well. The PP is impregnated well to CFs and good joining state was confirmed from Fig. 7.

Other hands, the over-moulded specimen with containing CNFs of 0.5 wt% (moulded at 240°C, route A) has completely different fracture morphology as shown in Fig. 8. In the PP at aperture of cloth and gaps between CFs at substrate part, CNFs are confirmed among the PP at high magnification. The CNFs may restrict the PP deformation by CNF networks since

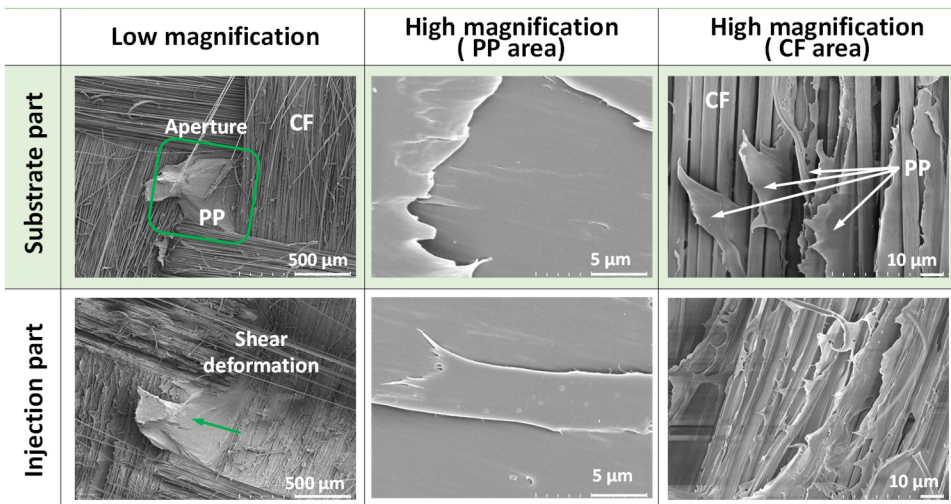


Figure 7: Fracture morphology of peeled surface on the substrate part (upper) and injection part (lower) for over-moulded sample without CNFs (moulded at 260°C, route A).

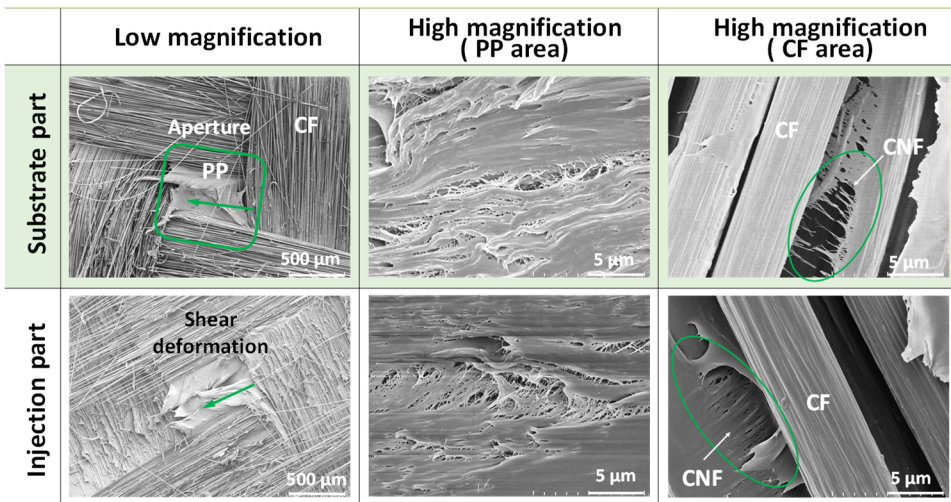


Figure 8: Fracture morphology of peeled surface on the substrate part (upper) and injection part (lower) for over-moulded sample with CNF of 0.5 wt% (moulded at 240°C, route A).

deformation length of PP at aperture decreased by adding CNFs. Surprisingly, the CNFs could confirm on the both sides even though CNFs added on only surface of substrate part. This proves that CNFs reinforce the PP at joining area and have interconnection role during shear deformation by lap-shear test. Thus, the CNF addition may improve the apparent shear strength of joining area by this mechanism.

#### 4 CONCLUSIONS

In this paper, we newly adopt CNFs at joining interface for improving joining strength through injection over-moulding. The joining strength was determined as apparent lap-shear strength of single-lap joint. The barrel temperature and runner route were varied for moulding the lap joint specimens in terms of resin temperature at joining area. As a result, lap-shear strength significantly increased as increasing barrel temperature due to promoting molecular diffusion of PP between resin layer of substrate and injection resin. In the influence of runner route on lap-shear strength, route A shows higher strength by compared with route B at barrel temperature of 240°C and 260°C, even though route B could carry melt PP to joining area with keeping higher resin temperature. This assumed that the flow behaviour of route B may show the corner flow, and the temperature distribution at joining area was inhomogeneous. Thus, the homogeneous flow behaviour and temperature distribution are necessary to improve lap-shear strength. However, the optimization of process parameters is necessary to get the enough temperature for fusion welding.

In the effect of CNF addition at joining interface, lap-shear strength and displacement at break significantly increased by adding the CNFs against the specific conditions. The reinforcement effect of CNFs exhibited above barrel temperature of 240°C in route A and barrel temperature of 260°C in route B, respectively. Finally, maximum lap-shear strength was 10.9 MPa in this experiment at the condition of CNF loading of 1.0 wt% and barrel temperature of 260°C in route A. By morphology assessment, CNFs could confirm at the both peeled surfaces. CNFs restrict the movement of PP molecular chain during shear deformation, and CNFs reinforce the fusion welded PP between injection resin and resin layer of substrate. In the future, resin temperature of joining area during over-moulding should be discussed more to obtain the maximum effect of CNF addition.

#### REFERENCES

- [1] Schricker, K., Diller, S. & Bergmann, J.P., Bubble formation in thermal joining of plastics with metals. *Procedia CIRP*, **74**, pp. 518–523, 2018.
- [2] Grefe, H., Kandula, M.W. & Dilger, K., Influence of the fibre orientation on the lap shear strength and fracture behaviour of adhesively bonded composite metal joints at high strain rates. *International Journal of Adhesion and Adhesives*, **97**, 102486, 2020.
- [3] Schulz, M., Janssen, H. & Brecher, C., Adaptive, connected production of hybrid thermoplastic prototypes. *Reinforced Plastics*, **63**(1), pp. 26–28, 2019.
- [4] Galvez, P. et al., Study of the behaviour of adhesive joints of steel with CFRP for its application in bus structures. *Composites Part B: Engineering*, **129**, pp. 41–46, 2017.
- [5] Ohishi, M., Ohtani, A. & Nakai, A., Effect of heater system on heating efficiency and interfacial properties between prepreg and injected part in hybrid molding. *Journal of Mechanical Engineering and Automation*, **7**(1), pp. 1–7, 2017.
- [6] Blok, L.G., Longana, M.L., Yu, H. & Woods, B.K.S., An investigation into 3D printing of fibre reinforced thermoplastic composites. *Additive Manufacturing*, **22**, pp. 176–186, 2018.
- [7] Prüß, H. & Vietor, T., Design for fiber-reinforced additive manufacturing. *The American Society of Mechanical Engineers Journal of Mechanical Design*, **137**(11), 111409, 2015.
- [8] Sugiyama, K., Matsuzaki, R., Ueda, M., Todoroki, A. & Hirano, Y., 3D printing of composite sandwich structures using continuous carbon fiber and fiber tension. *Composites Part A: Applied Science and Manufacturing*, **113**, pp. 114–121, 2018.



- [9] Holzinger, M., Blase, J., Reinhardt, A. & Kroll, L., New additive manufacturing technology for fibre-reinforced plastics in skeleton structure. *Journal of Reinforced Plastics and Composites*, **37**(20), pp. 1246–1254, 2018.
- [10] Fiorotto, M. & Lucchetta, G., Experimental investigation of a new hybrid molding process to manufacture high-performance composites. *International Journal of Material Forming*, **6**, pp. 179–185, 2013.
- [11] Joppich, T., Menrath, A. & Henning, F., Advanced molds and methods for the fundamental analysis of process induced interface bonding properties of hybrid, thermoplastic composites. *Procedia CIRP*, **66**, pp. 137–142, 2017.
- [12] Jiao, J., Xu, Z., Wang, Q., Sheng, L. & Zhang, W., CFRTP and stainless steel laser joining: Thermal defects analysis and joining parameters optimization. *Optics and Laser Technology*, **103**, pp. 170–176, 2018.
- [13] Li, Y. et al., Effect of laser heat input on the interface morphology during laser joining of CFRTP and 6061 aluminum alloy. *Journal of Manufacturing Processes*, **50**, pp. 366–379, 2020.
- [14] Jiao, J. et al., Laser direct joining of CFRTP and aluminium alloy with a hybrid surface pre-treating method. *Composites Part B: Engineering*, **173**, 106911, 2019.
- [15] Wu, L.H., Nagatsuka, K. & Nakata, K., Direct joining of oxygen-free copper and carbon-fiber-reinforced plastic by friction lap joining. *Journal of Materials Science and Technology*, **34**(1), pp. 192–197, 2018.
- [16] Goto, K., Imai, K., Arai, M. & Ishikawa, T., Shear and tensile joint strengths of carbon fiber-reinforced thermoplastics using ultrasonic welding. *Composites Part A: Applied Science and Manufacturing*, **116**, pp. 126–137, 2019.
- [17] Lucchetta, G., Marinello, F. & Bariani, P.F., Aluminum sheet surface roughness correlation with adhesion in polymer metal hybrid overmolding. *CIRP Annals*, **60**(1), pp. 559–562, 2011.
- [18] Kimura, F., Kadoya, S. & Kajihara, Y., Effects of molding conditions on injection molded direct joining under various surface fine-structuring. *The International Journal of Advanced Manufacturing Technology*, **101**, pp. 2703–2712, 2019.
- [19] Kimura, F., Kadoya, S. & Kajihara, Y., Effects of molding conditions on injection molded direct joining using a metal with nano-structured surface. *Precision Engineering*, **45**, pp. 203–208, 2016.
- [20] Li, X. et al., Aluminum/polypropylene composites produced through injection molding. *Journal of Materials Processing Technology*, **255**, pp. 635–643, 2018.
- [21] Stormonth-Darling, J.M. & Gadegaard, N., Injection moulding difficult nanopatterns with hybrid polymer inlays. *Macromolecular Materials and Engineering*, **297**, pp. 1075–1080, 2012.
- [22] Garcia, E.J., Wardle, B.L., Hart, A.J. & Yamamoto, N., Fabrication and multifunctional properties of a hybrid laminate with aligned carbon nanotubes grown in situ. *Composites Science and Technology*, **68**(9), pp. 2304–2041, 2008.
- [23] Wicks, S.S., de Villoria, R.G. & Wardle, B.L., Interlaminar and intralaminar reinforcement of composite laminates with aligned carbon nanotubes. *Composites Science and Technology*, **70**(1), pp. 20–28, 2010.
- [24] Veedu, V. et al., Multifunctional composites using reinforced laminae with carbon-nanotube forests. *Nature Materials*, **5**, pp. 457–462, 2006.
- [25] Matsumoto, K., Ishikawa, T. & Tanaka, T., A novel joining method by using carbon nanotube-based thermoplastic film for injection over-molding process. *Journal of Reinforced Plastics and Composites*, **38**(13), pp. 616–627, 2019.

